

CHARACTERIZATION AND SINTERING PROPERTIES OF HYDROXYAPATITE BIOCERAMICS SYNTHESIZED FROM CLAMSHELL BIOWASTE

CHUI KIM NG^{1*}, KIT YEE SARA LEE², CHIN HONG TAN¹, SINGH RAMESH^{3,4},
CHEN HUNT TING⁵, YEA DAT CHUAH⁶, CHOU YONG TAN³,
AND UBENTHIRAN SUTHARSINI⁷

¹Centre for Advanced Materials, Department of Materials Engineering, Faculty of Engineering & Technology, Tunku Abdul Rahmani University College, 53300 Kuala Lumpur, Malaysia

²Center of Systematic Innovation Research, Department of Mechanical Engineering, Faculty of Engineering & Technology, Tunku Abdul Rahmani University College, 53300 Kuala Lumpur, Malaysia

³Centre of Advanced Manufacturing & Material Processing (AMMP), Department of Mechanical Engineering, Faculty of Engineering, University of Malaya, 50603 Kuala Lumpur, Malaysia

⁴Department of Mechanical Engineering, Faculty of Engineering, Universiti Teknologi Brunei, Tunku Highway, Gadong BE1410, Brunei Darussalam

⁵Department of Mechanical and Materials & Manufacturing Engineering, Lee Kong Chian Faculty of Engineering and Science, Universiti Tunku Abdul Rahman, Jalan Sungai Long, Bandar Sungai Long, Cheras, 43000 Kajang, Selangor Darul Ehsan, Malaysia

⁶Department of Mechanical, Materials and Manufacturing (M3) Engineering, University of Nottingham Malaysia, Jalan Broga, 43500 Semenyih, Selangor Darul Ehsan, Malaysia.

⁷Department of Physics, University of Jaffna, Jaffna JA 40000, Sri Lanka

*Corresponding author: ngck@tarc.edu.my

(Received: 9th July 2021; Accepted: 8th November 2021; Published on-line: x xxxx 2022)

ABSTRACT: Hydroxyapatite (HA) is a type of calcium phosphate-based bioactive ceramic that resembles the mineral phase of bone and teeth with great potential for bone substitution and biomedical implants. Biogenic-derived HA emerges as a cheap and eco-sustainable alternative to improve waste utilization. However, hydroxyapatite has limited applications due to its apparent brittleness, thus prompted investigation for enhanced sintering properties. In the present study, the combination of calcination and chemical precipitation technique was used to extract hydroxyapatite (HA) from the ark clamshells (*Anadara granosa*). The method had successfully produced HA powder with a Ca/P ratio of 1.6 and characteristic bands corresponded to pure HA via Fourier Transform Infrared Spectroscopy (FTIR). The synthesized HA powder was then sintered at temperatures ranging from 1200 °C to 1300 °C, followed by mechanical evaluation on the density, Vickers hardness, fracture toughness and grain size. It was revealed that the samples sintered at 1250 °C achieved a relative density of ~88%, Vickers hardness of 5.01 ± 0.39 GPa, fracture toughness of 0.88 ± 0.07 MPa.m^{1/2} and average grain size of ~3.7 μm. Overall, the results suggest that ark clamshells synthesized HA (ACS) had the potential to be used as functional bioceramics for biomedical applications.

ABSTRAK: Hydroxyapatite (HA) adalah sejenis seramik bioaktif berasaskan kalsium fosfat yang menyerupai fasa mineral tulang dan gigi dengan potensi besar untuk penggantian tulang dan implan bioperubatan. HA yang berasal dari biogenik muncul sebagai alternatif yang murah dan eko-lestari yang akan menambah sisa penggunaan. Walau bagaimanapun, hidroksiapatit mempunyai aplikasi yang terhad kerana kerapuhannya yang ketara, oleh demikian mendorong penyelidikan untuk meningkatkan sifat sintering. Dalam kajian ini, kombinasi teknik kalsinasi dan pemendakan kimia telah digunakan untuk mengekstrak

hidroksiapatit (HA) dari kerang bahtera (*Anadara granosa*). Kaedah ini telah berjaya menghasilkan serbuk HA dengan nisbah 1.6 Ca/P dan jalur puncak sepadan dengan HA tulen melalui spektroskopi inframerah transformasi Fourier (FTIR). Serbuk HA yang disintesis kemudian disinter pada suhu antara 1200 ° C hingga 1300 ° C, diikuti dengan penilaian mekanikal mengenai ketumpatan, kekerasan Vickers, ketahanan patah dan ukuran bijirin. Hasil ujian menunjukkan bahawa sampel yang disinter pada suhu 1250 ° C mencapai ~88% ketumpatan relatif, kekerasan Vickers 5.01 ± 0.39 GPa, ketahanan patah 0.88 ± 0.07 MPa.m^{1/2} dan ukuran butiran purata ~3.7 µm. Secara keseluruhan, hasilnya menunjukkan bahawa ark clamshells synthesized HA (ACS) berpotensi digunakan sebagai bioceramics fungsional untuk aplikasi bioperubatan.

KEY WORDS: *Hydroxyapatite, bioceramics, chemical synthesis, calcination, sintering*

1. INTRODUCTION

Hydroxyapatite (HA) with a chemical formula of $\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$, is a type of calcium phosphate-based ceramics that consists of the main mineral constituent to human bones and teeth, which is widely used in dental and orthopedic applications. The conventional methods to synthesize HA are solid-state, mechanochemical, chemical precipitation, hydrolysis, sol-gel, hydrothermal, emulsion, sonochemical, high-temperature processes or a combination of few techniques [1]. Among these methods, wet-chemical precipitation is the most promising and low-cost techniques [2, 3].

In recent years, biowaste-derived HA has attracted attention as numerous food wastes such as bones, eggshells and seafood shells had piled up in landfill globally. Specifically, shell wastes such as oyster, mussel, scallops, clams and cockle are discarded in an abundant amount. Million tons of shell wastes had been discarded and piled up in landfill in China, Taiwan, Spain, South Korea, Peru, Indonesia, Nigeria and Malaysia [4-7]. Instead, these shell wastes could be utilized to synthesize HA owing to the rich calcium carbonate (CaCO_3) content [8-10]. Typically, HA has been successfully synthesized via hydrothermal synthesis method by utilizing various species of clamshells such as *Strombus gigas*, *Tridacna gigas* [11], *Venerupis* [12], *Corbicula* [13, 14], *Mercenaria* [15], and *Anadara granosa* [16]. However, majority of the studies did not report the mechanical properties of sintered HA. In the current study, *Anadara granosa* clamshell will be used as the calcium precursor to synthesize natural HA powder, followed by characterization of its properties at various sintering temperatures.

2. MATERIALS AND METHODS

2.1. Synthesis of powder

Biogenic sources such as seashells or eggshells are good natural resources of calcium precursor for the synthesis of HA bioceramics. In this study, the *Anadara granosa* clamshells collected from peninsular Malaysia were used as the starting materials to synthesize HA. The as-received clamshells were washed thoroughly, rinsed with distilled water, and dried in an oven at 80°C for one hour. The dried clamshells were then crushed, ground and sieved through a 300 µm test sieve. This is followed by calcination at 1000 °C for four hours in the electrical furnace (Carbolite Gero, UK), to transform calcium carbonate (CaCO_3) into calcium oxide (CaO).

Fig. 1 depicts the flow chart of the HA synthesis process via wet chemical precipitation technique. First of all, 0.25 M of calcium precursor to 0.15 M of phosphorus precursor was

employed to achieve stoichiometric HA with the calcium/phosphorus (Ca/P) concentration ratio of 1.67. 2.8 g of CaO powder was then added in 200 ml of distilled water to formulate the $\text{Ca}(\text{OH})_2$ solution as the calcium precursor. The solution was subsequently magnetic stirred at 400 rpm for an hour and maintained at pH 12. On the other hand, the 2.05 ml concentrated H_3PO_4 (phosphorus precursor) was diluted into 200 ml of distilled water, stirred and kept at about pH 2. Subsequently, the prepared H_3PO_4 solution was then added dropwise into $\text{Ca}(\text{OH})_2$ solution to begin the titration process, continued with a vigorous stirring at 700 rpm for 30 minutes. The NH_4OH solution was then added to adjust the pH to 10. This is followed by the magnetic stirring at 500 rpm for an hour after the titration process and aged for 21 hours (to form white precipitate). Vacuum filtration was subsequently performed on the precipitates using an electrical aspirator pump (Jerio Tech, Korea). Finally, the precipitate was dried at an oven at 100 °C for 16 hours, crushed and sieved through a 300 μm test sieve to obtain ark clamshells synthesized HA (ACS) powder.

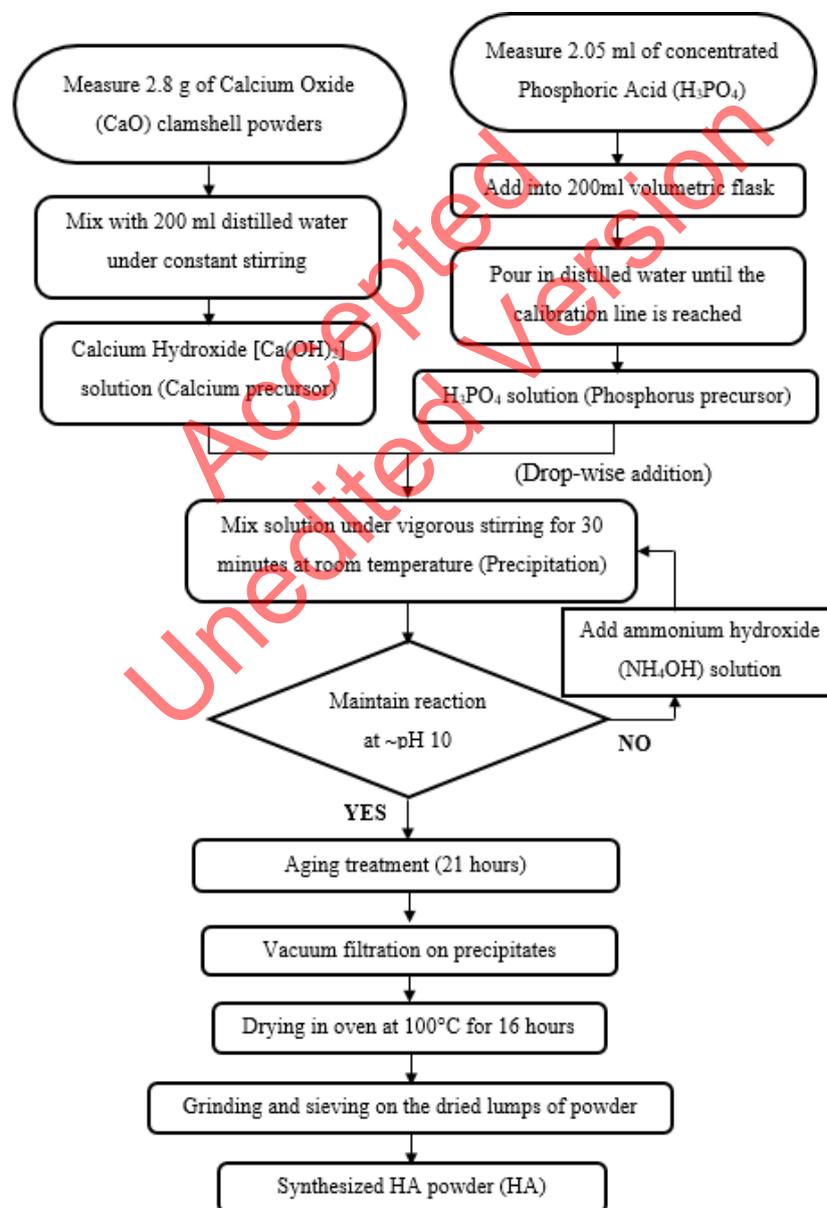


Fig. 1. Flow chart of the HA synthesis process via wet chemical precipitation technique

2.2 Sample preparation

The ACS synthesized HA powders were compacted into 20 mm disc samples (Fig. 2) by a hydraulic press machine (Enerpac, USA) at 1000 psi, which was set at a pressure lower than 3000 psi as recommended by Mel et al. [17]. The green samples were then conventionally sintered (Carbolite Gero, UK) at 1200 °C, 1250 °C and 1300 °C for two hours with a ramp rate of 10 °C/min. The dimension of the green and as-sintered samples was recorded with a digital Vernier caliper (Mitutoyo, Japan) for the shrinkage measurements. Prior to characterization, the sintered disc samples were ground with silicon carbide (SiC) sandpapers and polished to achieve a 1 µm optical reflective surface.

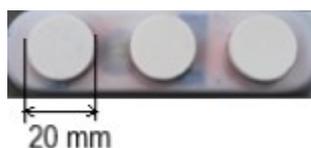


Fig. 2. HA green samples

2.3 Characterization and mechanical property evaluation

A Fourier transform infrared (FTIR) Spectrum 65 Spectrometer (Perkin Elmer Inc., USA) was used to identify the functional groups and composition that present in the synthesized powder, at the scan range of 650 to 4000 cm^{-1} . Differential scanning calorimetric (DSC)/Thermogravimetric analysis (TGA) (TA Instruments, USA) was employed to determine the weight loss and phase change of synthesized HA powder, from room temperature to 1400 °C, with a heating rate of 10 °C/min under nitrogen gas environment. Bulk density measurement was also performed on the sintered samples using the Archimedes' principle, by taking the theoretical density of HA as 3.156 g/cm^3 . The microstructure of synthesized and sintered samples was examined via scanning electron microscopy (SEM) (SEC Co. Ltd., Korea). Energy dispersive X-ray (EDX) spectroscopy was used to determine the Ca/P ratio of the synthesized and sintered samples. The grain size of the sintered samples was measured using the linear intercept method according to ASTM E112-96. Vickers hardness of the sintered samples was evaluated via micro-hardness tester (Bowers ESEWAY, UK), with an applied load of 200 gf at a loading time of 10 seconds based on ASTM E384-99. For each sample, at least five indentations were used to obtain the average hardness and to calculate the standard deviation value. Fracture toughness was also obtained via the relationship derived by Niihara et al. [18].

3. RESULTS AND DISCUSSION

3.1 FTIR analysis of ACS synthesized HA powder

The functional groups in the ACS synthesized HA powder were identified using FTIR and the spectrum is shown in Fig. 3. The result confirms that the synthesized powder exhibited the typical spectrum of pure HA powder, with the chemical groups of phosphate group (PO_4^{3-}), hydroxyl groups (OH^-) and carbonate groups (CO_3^{2-}). The distinctive peaks at 1025 cm^{-1} and 1087 cm^{-1} are corresponding to the PO_4^{3-} (ν_3), while the peak at 962 cm^{-1} corresponds to the PO_4^{3-} (ν_1). On the other hand, weak characteristic peaks observed at 3350 cm^{-1} and 3570 cm^{-1} could be related to the OH^- group. The FTIR peaks exhibited key characteristics of HA phase.

The peaks at 1456, 1420 cm^{-1} and 874 cm^{-1} show the presence of CO_3^{2-} in the samples. Similar carbonate bands were also reported in previous studies [19-20].

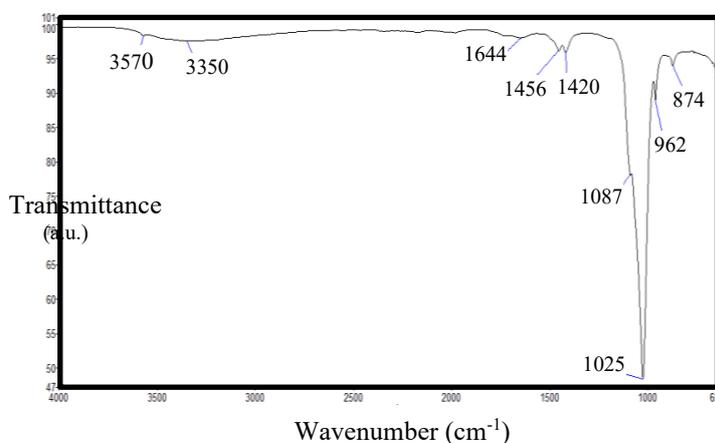


Fig. 3. FTIR spectrum of ACS synthesized HA powder

3.2 EDX analysis

Fig. 4 shows that the EDX spectrums of ACS synthesized and sintered HA samples consist of three main elemental constituents of HA bioceramics, which are calcium (Ca), phosphorus (P) and oxygen (O). From the atomic percentage (At %), the calculated Ca/P ratio of synthesized biogenic HA powder is 1.60, while the sintered HA bioceramics increased to ~ 1.88 when sintered at 1200 $^{\circ}\text{C}$ and 1250 $^{\circ}\text{C}$, and reached at 1.97 when sintered at 1300 $^{\circ}\text{C}$. The obtained Ca/P ratio from this work deviated from the theoretical value for pure stoichiometric HA of 1.67. Similar observation was reported by Ramesh et al. [21]

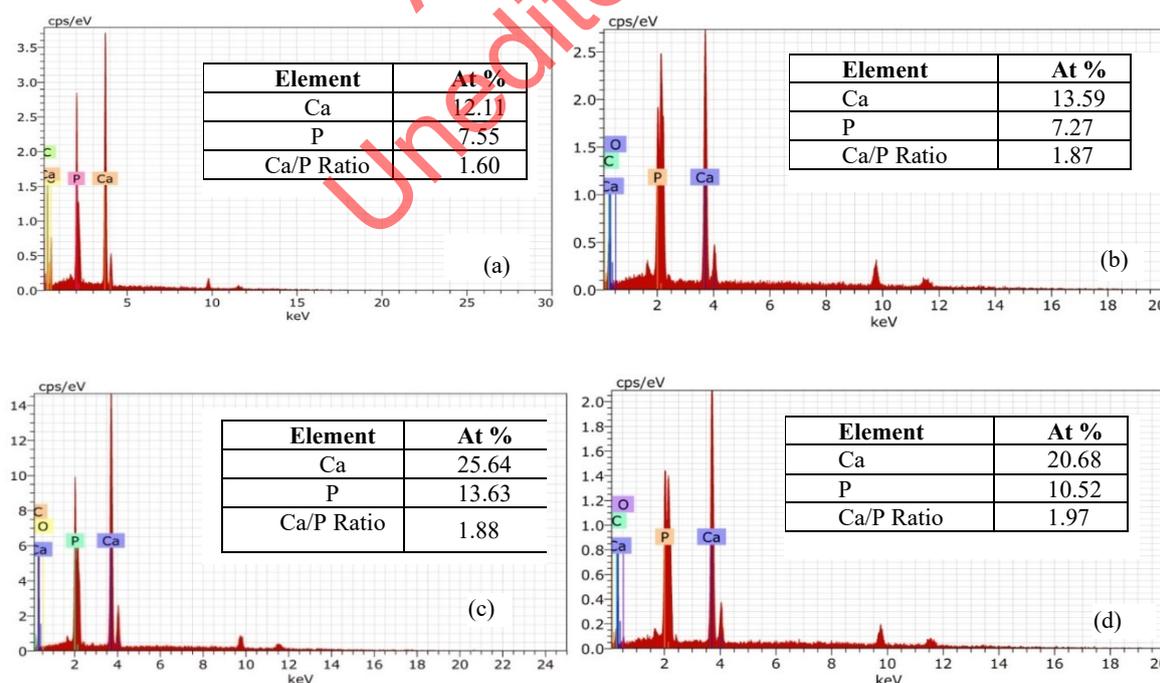


Fig. 4. EDX spectrum ACS (a) synthesized HA powder, sintered HA at (b) 1200 $^{\circ}\text{C}$, (c) 1250 $^{\circ}\text{C}$, and (d) 1300 $^{\circ}\text{C}$.

3.3 Microstructural and grain size analysis

Fig. 5 (a) shows the SEM micrograph of the ACS synthesized HA powder, which consists of large agglomerates. The microstructural evolution of the ACS sintered HA ceramics is presented in Fig. 5 (b)-(d). The SEM investigation revealed that the average grain size for the sintered HA samples increases with the increase of sintering temperatures. The results show a gradual increase in grain size from 2.14 μm at 1200 $^{\circ}\text{C}$ to 3.70 μm at 1250 $^{\circ}\text{C}$. As the sintering temperature increased to 1300 $^{\circ}\text{C}$, the grain size dramatically increased to 6.44 μm . Accelerated grain growth in HA samples sintered beyond 1250 $^{\circ}\text{C}$ implied a change in phase stability of HA.

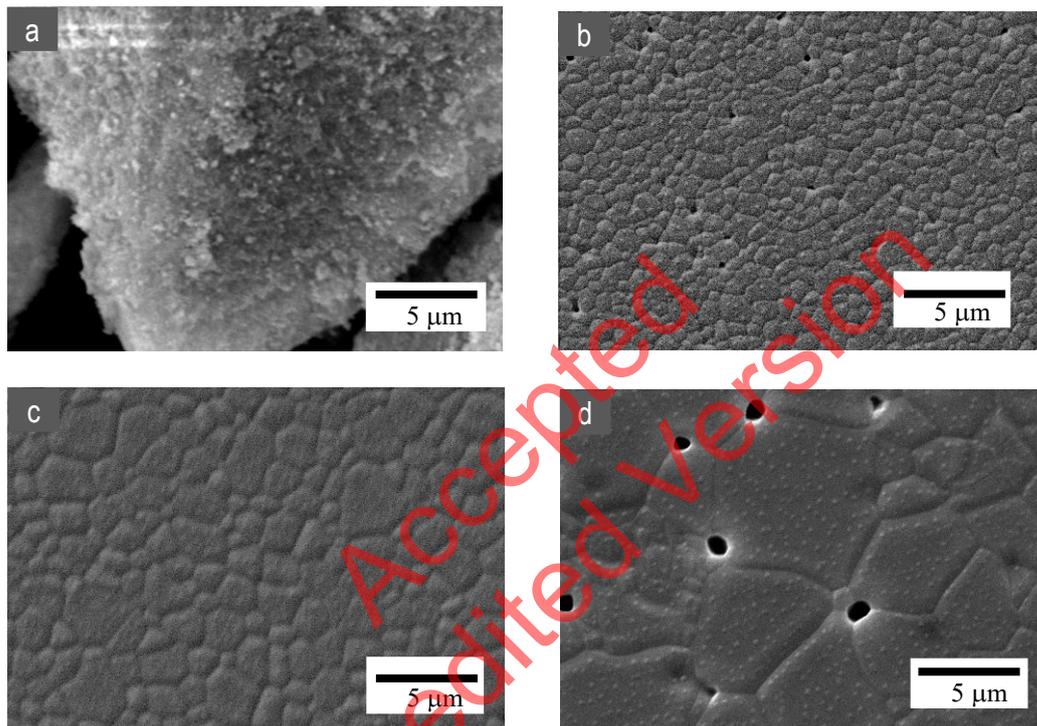


Fig. 5. SEM images of (a) ACS synthesized HA powder and sintered HA at (b) 1200 $^{\circ}\text{C}$, (c) 1250 $^{\circ}\text{C}$, and (d) 1300 $^{\circ}\text{C}$.

3.4 Thermal stability analysis

Fig. 6 shows the differential scanning calorimetric (DSC)/ thermogravimetric analysis (TGA) measurement of the ACS synthesized HA powder. At 300 $^{\circ}\text{C}$, a pronounced weight loss of ~5.3% was observed from total weight loss of 7.6% of the HA sample. The weight loss could be ascribed to the evaporation of physically adsorbed water molecules. With additional heating upon 500 $^{\circ}\text{C}$, the insignificant weight loss (~0.75%) is attributed to the release of interstitial water molecule in the crystal lattice of HA. An endothermic peak at ~1000 $^{\circ}\text{C}$ can be postulated as dehydroxylation and decarboxylation of the HA powder. Weight loss at higher temperatures may be due to the dissociation of HA to tricalcium phosphate (TCP) and tetracalcium phosphate (TTCP). The decomposition of HA phase is believed to cause the increased in the average grain size and reduced the mechanical properties of the HA.

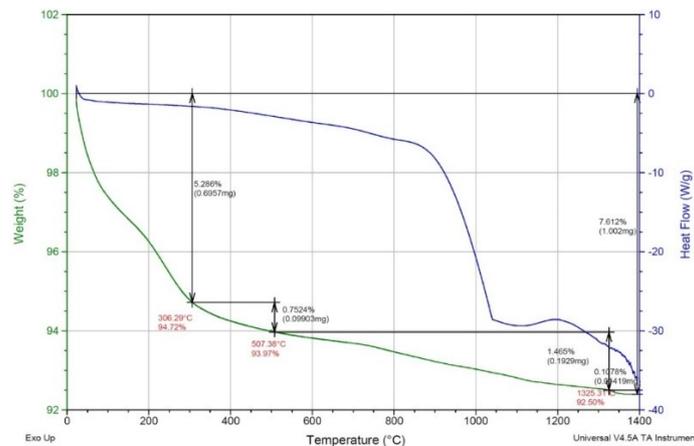


Fig. 6: DSC/ TGA plot of the ACS synthesized HA powder.

3.5 Mechanical properties

The effect of sintering temperature on the relative density, Vickers hardness and fracture toughness of HA ceramics are presented in Table 1. The density of ACS sintered HA increased from 83.8% at 1200 °C to 88% at 1250 °C. A slight decrease in density (86.7%) was observed when the sintering temperature increased to 1300 °C. The result is in agreement with the grain growth of the sintered HA as shown in the SEM images. On the other hand, the Vickers hardness of the sintered HA increased from 4.35 ± 0.43 GPa at 1200 °C to a maximum of 5.01 ± 0.39 GPa at 1250 °C. When the sintering temperature reached 1300 °C, the Vickers hardness was reduced to 4.03 ± 0.35 GPa, which is corresponding with the reduction in relative density and the grain growth of the sintered HA. This is in agreement with Aminzare and co-authors, where the Vickers hardness of the sintered biomimetic-synthesized HA decreased from 2.52 GPa to 2.23 GPa when sintered at 1250 °C and 1300 °C, respectively [22].

In the current study, the fracture toughness exhibited similar trends as the hardness, i.e. the fracture toughness increased from 0.67 ± 0.20 MPa.m^{1/2} to a maximum of 0.88 ± 0.07 MPa.m^{1/2}, when sintered at 1200 °C and 1250 °C, respectively. This is followed by a decreased to 0.71 ± 0.10 MPa.m^{1/2} when the sintering temperature reached 1300 °C. Similarly, the decreased fracture toughness at 1300 °C is related to the decrease of relative density. It is postulated that the reduced density and mechanical properties at 1300 °C was due to the decomposition of HA phase at a high sintering temperature regime (>1250 °C) [22-23]. The results also show that calcium-rich HA with the Ca/P ratio of 1.88 possessed an overall higher density and mechanical properties as compared to HA with Ca/P ratio of 1.97.

Table 1: The properties of ACS sintered HA

Sintering temp/ holding time	Grain size (μm)	Relative density (%)	Vickers Hardness (GPa)	Fracture toughness (MPa.m ^{1/2})
1200 °C/ 2 hrs	2.14	83.8	4.35 ± 0.43	0.67 ± 0.20
1250 °C/ 2 hrs	3.70	88.0	5.01 ± 0.39	0.88 ± 0.07
1300 °C/ 2 hrs	6.44	86.7	4.03 ± 0.35	0.71 ± 0.10

4. CONCLUSION

The present study revealed that ACS synthesized HA samples were successfully synthesized via the calcination and wet chemical precipitation using ark clamshells (*Anadara granosa*) as the calcium precursor. The results also show that ACS sintered HA with the Ca/P ratio of 1.88 possessed a higher density (~88%) and mechanical properties (Vickers hardness of ~5 GPa and fracture toughness of ~0.88 MPa.m^{1/2}) when sintered at 1250 °C, which shows that the phase stability of HA was retained up to 1250 °C and the decomposition of HA to TCP and TTCP occurred above 1250 °C. The finding of this study would promote the recycling and reuse of the animal shells or bones to convert biowaste into value added biomedical products which would help in attaining Sustainable Development Goal targets. Future research would encompass further works on two-step or hybrid sintering routes to produce finer microstructure with enhanced mechanical properties.

REFERENCES

- [1] Sadat-Shojai M, Khorasani MT, Dinpanah-Khoshdargi E, Jamshidi A. (2013) Synthesis methods for nanosized hydroxyapatite with diverse structures. *Acta Biomaterialia*, 9(8):7591-7621. <https://doi.org/10.1016/j.actbio.2013.04.012>
- [2] Hongquan Z, Yuhua Y, Youfa W, Shipu L. (2003) Morphology and formation mechanism of hydroxyapatite whiskers from moderately acid solution. *Materials Research*, 6:111-115. Retrieved from <https://www.scielo.br/pdf/mr/v6n1/v6n1a20.pdf>
- [3] Hablee, S, Sopyan I, Mel, M, Salleh, H.M. and Rahman, MM. (2018) Effect of poly (ethylene glycol) on the injectability, setting behavior and mechanical properties of calcium phosphate bone cement. *IIUM Engineering Journal*, 19(2):192-202. <https://journals.iium.edu.my/ejournal/index.php/iiumej/article/view/913>
- [4] Mo KH, Alengaram UJ, Jumaat MZ, Lee SC, Goh WI, Yuen CW. (2018) Recycling of seashell waste in concrete: A review. *Construction and Building Materials*, 162: 751-764. <https://doi.org/10.1016/j.conbuildmat.2017.12.009>
- [5] Hembrick-Holloman V, Samuel T, Mohammed Z, Jeelani S, Rangari VK. (2020) Ecofriendly production of bioactive tissue engineering scaffolds derived from egg- and sea-shells. *Journal of Materials Research and Technology*, 9(6):13729-13739. <https://doi.org/10.1016/j.jmrt.2020.09.093>
- [6] Saharudin SH, Shariffuddin JH, Nordin NI. (2017). Biocomposites from (*Anadara granosa*) shells waste for bone material applications. *IOP Conference Series: Materials Science and Engineering*, 257:012061. Retrieved from <https://iopscience.iop.org/article/10.1088/1757-899X/257/1/012061/pdf>
- [7] Musa B, Raya I, Natsir H. (2016) Synthesis and Characterizations of Hydroxyapatite Derived Blood Clam Shells (*Anadara granosa*) and Its Potency to Dental Remineralizations. 12(4):527-38. Retrieved from https://www.ripublication.com/ijac16/ijacv12n4_04.pdf
- [8] Bee SL, Hamid ZA. (2020) Hydroxyapatite derived from food industry bio-wastes: Syntheses, properties and its potential multifunctional applications. *Ceramics International*, 46(11, Part A): 17149-17175. <https://doi.org/10.1016/j.ceramint.2020.04.103>
- [9] Pu'ad NM, Koshy P, Abdullah HZ, Idris MI, Lee TC. (2019) Syntheses of hydroxyapatite from natural sources. *Heliyon*, 5(5):e01588. <https://doi.org/10.1016/j.heliyon.2019.e01588>
- [10] Núñez D, Elgueta E, Varaprasad K, Oyarzún P. (2018) Hydroxyapatite nanocrystals synthesized from calcium rich bio-wastes. *Materials Letters*, 230: 64-68. <https://doi.org/10.1016/j.matlet.2018.07.077>
- [11] Vecchio KS, Zhang X, Massie JB, Wang M, Kim CW. (2007) Conversion of bulk seashells to biocompatible hydroxyapatite for bone implants. *Acta Biomaterialia*, 3(6): 910-918. <https://doi.org/10.1016/j.actbio.2007.06.003>

- [12] Bramhe S, Kim TN, Balakrishnan A, Chu MC. (2014) Conversion from biowaste Venerupis clam shells to hydroxyapatite nanowires. *Materials Letters*, 135:195-198. <https://doi.org/10.1016/j.matlet.2014.07.137>
- [13] Onoda H, Yamazaki S. (2016) Homogenous hydrothermal synthesis of calcium phosphate with calcium carbonate and corbicula shells. *Journal of Asian Ceramic Societies*, 4(4): 403-406. <https://doi.org/10.1016/j.jascer.2016.10.001>
- [14] Alif MF, Aprillia W, Arief S. (2018) A hydrothermal synthesis of natural hydroxyapatite obtained from Corbicula moltkiana freshwater clams shell biowaste. *Materials Letters*, 230: 40-43. <https://doi.org/10.1016/j.matlet.2018.07.034>
- [15] Pal A, Nasker P, Paul S, Chowdhury AR, Sinha A, Das M. (2019) Strontium doped hydroxyapatite from Mercenaria clam shells: Synthesis, mechanical and bioactivity study. *Journal of the Mechanical Behavior of Biomedical Materials*, 90:328-336. <https://doi.org/10.1016/j.jmbbm.2018.10.027>
- [16] Azis Y, Jamarun N, Arief S, Nur H. (2015) Facile synthesis of hydroxyapatite particles from cockle shells (*Anadaragranosa*) by hydrothermal method. *Oriental journal of chemistry*, 31:1099-1105.
- [17] Mel M, Abdeen FR, and Sopyan I. (2011). Fabrication of Ceramic Membrane Chromatography for Biologics Purification. *IIUM Engineering Journal*, 12(4).
- [18] Niihara K, Morena R, Hasselman DP. (1982) Evaluation of K_{Ic} of brittle solids by the indentation method with low crack-to-indent ratios. *Journal of Materials Science Letters*, 1(1):13-16.
- [19] Ramesh S, Natasha AN, Tan CY, Bang LT, Ching C.Y Chandran H. (2016) Direct conversion of eggshell to hydroxyapatite ceramic by a sintering method. *Ceramics international*, 42(6),7824-7829. <https://doi.org/10.1016/j.ceramint.2016.02.015>
- [20] Kamalanathan P, Ramesh S, Bang LT, Niakan A, Tan CY, Purbolaksono J, Chandran H, Teng WD. (2014) Synthesis and sintering of hydroxyapatite derived from eggshells as a calcium precursor. *Ceramics International*, 40(10), 16349-16359. <https://doi.org/10.1016/j.ceramint.2014.07.074>
- [21] Ramesh S, Loo ZZ, Tan CY, Chew WK, Ching YC, Tarlochan F, Chandran H, Krishnasamy S, Bang LT, Sarhan AA (2018) Characterization of biogenic hydroxyapatite derived from animal bones for biomedical applications. *Ceramics International*, 44(9), 10525-10530. <https://doi.org/10.1016/j.ceramint.2018.03.072>
- [22] Aminzare M, Eskandari A, Baroonian MH, Berenov A, Hesabi ZR, Taheri M, Sadrnezhad SK. (2013) Hydroxyapatite nanocomposites: Synthesis, sintering and mechanical properties. *Ceramics International*. 39(3):2197-2206. <https://doi.org/10.1016/j.ceramint.2012.09.023>
- [23] Ramesh S, Tan CY, Hamdi M, Sopyan I, Teng WD. (2007) The influence of Ca/P ratio on the properties of hydroxyapatite bioceramics. In *International conference on smart materials and nanotechnology in engineering*. International Society for Optics and Photonics. 6423, 64233A.